

Orientation-Dependent Transparency of Metallic Interfaces

P. X. Xu,¹ K. Xia,¹ M. Zwierzycki,^{2,3} M. Talanana,² and P. J. Kelly²

¹*State Key Laboratory for Surface Physics, Institute of Physics,*

Chinese Academy of Sciences, P. O. Box 603, Beijing 100080, China.

²*Faculty of Science and Technology and MESA⁺ Institute for Nanotechnology,*

University of Twente, P.O. Box 217, 7500 AE Enschede, The Netherlands

³*Max-Planck-Institut für Festkörperforschung, Heisenbergstr. 1, D-70569 Stuttgart, Germany.*

(Dated: February 6, 2008)

As devices are reduced in size, interfaces start to dominate electrical transport making it essential to be able to describe reliably how they transmit and reflect electrons. For a number of nearly perfectly lattice-matched materials, we calculate from first-principles the dependence of the interface transparency on the crystal orientation. Quite remarkably, the largest anisotropy is predicted for interfaces between the prototype free-electron materials silver and aluminium for which a massive factor of two difference between (111) and (001) interfaces is found.

PACS numbers: 71.15-m, 72.10.Bg, 72.25.Ba, 73.40.Cg, 73.40-c, 75.47.De

A recurring theme in condensed matter physics in the last twenty years has been the discovery of new physical effects and properties in systems with reduced dimensions; the prospect of exploiting these effects and properties in logical processing, sensing and storage devices is an important driving force behind nano-science and -technology. In semiconductors, the electronic structures of the electrons responsible for conduction can be described using simple models. The same is not true of the ferromagnetic transition metals which form the basis for magnetoelectronics. It is the non-trivial spin-dependence of the transmission and reflection of electrons at magnetic interfaces which provides the key to understanding phenomena such as oscillatory exchange coupling, giant- and tunneling- magnetoresistance, spin transfer torque, spin-pumping and spin injection [1]. For well-studied material combinations such as Co/Cu and Fe/Cr, modest spin-dependence of the interface transmission [2, 3, 4] of the order of 10-20% is sufficient to account for experimental observations [5].

However, the confrontation of theory and experiment just referred to is at best indirect and model-dependent. Even though the theory of transport in small structures is formulated in terms of transmission and reflection matrices [6], measuring interface transparencies directly has proven quite difficult [7]. To identify interfaces suitable for experimental study, we have undertaken a systematic materials-specific study of the orientation dependence of the interface transmission between pairs of isostructural metals whose lattice constants match within a percent or so in the hope that it will prove possible to grow such interfaces epitaxially.

One of the metal pairs we studied was Al/Ag. Both metals have the fcc crystal structure and their lattice constants are matched within 1%. Aluminium is a textbook [8] example of a system well described by the (nearly) free electron model. Silver, also usually assumed to be a free electron-like material, is a noble metal with high conduc-

tivity which is frequently used for electrical contacting. We found that in spite of the simplicity of both metals' electronic structures the transmission through Al/Ag interfaces can differ quite significantly from the predictions of the free electron model. In particular, between (111) and (001) orientations we find a factor 2 difference in interface transmission for clean Al/Ag interfaces. For free electrons the anisotropy should vanish. Our result is insensitive to interface disorder. We identify a new factor responsible for this difference which is not related to the standard velocity- [9, 10] or symmetry-mismatch [11, 12] mechanisms.

A free electron description of interface scattering, in which the effect of the crystal potential on transport is completely neglected, underlies the BTK theory [13] used to interpret [9, 10] Andreev reflection (AR) experiments. Point contact AR experiments are increasingly used to identify the pairing symmetry of superconductors and, in the field of magnetoelectronics, to determine the polarization of magnetic materials [14, 15]. Our finding that the electronic structure can have such a large effect on the interface transmission, implies that experiments should be analysed using more sophisticated models.

Our study was based upon first-principles calculations of the interface electronic structure performed within the framework of density functional theory (DFT) and the local spin density approximation (LSDA). Bulk and interface potentials were determined self-consistently using the tight binding linearized muffin tin orbital (TB-LMTO) [16] surface Green's function method [17]. We assumed common lattice constants for both metals of a given structure e.g. $a_{Al} = a_{Ag} = 4.05 \text{ \AA}$. The potentials obtained in this way were used as input to a TB-MTO wavefunction-matching [4, 12] calculation of the transmission and reflection coefficients between Bloch states on either side of the interface. The efficiency of this approach is such that interface disorder can be modelled using large lateral supercells. For disordered systems,

the potentials were calculated using the layer CPA (coherent potential approximation). The results of the calculations for a number of lattice-matched materials are summarized in Table I.

The Sharvin conductances, G_A and G_B , reported in the third and fourth columns of Table I are proportional to the number of states at the Fermi level propagating in the transport direction. They are properties of the bulk materials which are determined by the area of the Fermi surface projections and are a measure of the current-carrying capacity of the conductor in the ballistic regime. The largest intrinsic orientation dependence, seen to be about 13 %, is found for Mo; for Al and Ag, respectively, it is less than 8% and 5%.

The interface transmission in column five of Table I is expressed as a conductance, $G_{A/B} = e^2/h \sum_{\mu\nu} T_{\mu\nu}$, where $T_{\mu\nu}$ is the probability for the incoming state ν in material A to be transmitted through the interface into the outgoing state μ in material B. For most pairs of materials [18], the orientation dependence of $G_{A/B}$ is modest ($\sim 15\%$ for Mo/W) and the interface conduc-

TABLE I: Sharvin conductances and interface transmissions in units of $10^{15}\Omega^{-1}m^{-2}$, interface resistances SR [2, 4] for ideal (and, in brackets, for disordered) interfaces in units of $10^{-15}\Omega m^2$. S is the area of the sample for which R is measured. Interface disorder was modelled in 10×10 lateral supercells with two layers of 50-50 alloy. The largest uncertainty between different configurations of disorder is about 2.3%. The values given are for a single spin. For the pairs of materials and orientations indicated by a (*), comparison of the interface resistances shown in the last two columns with experimental values extracted from measurement on multilayers by the MSU group [5, 7] yields reasonable quantitative agreement [2, 4, 12].

A/B		G_A	G_B	$G_{A/B}$	$2SR$
Al/Ag	(111)	0.69	0.45	0.41 (0.36)	0.64 (0.92)
$a_{fcc} = 4.05 \text{ \AA}$	(110)	0.68	0.47	0.30 (0.32)	1.60 (1.39)
	(001)	0.73	0.45	0.22 (0.24)	2.82 (2.37)
Al/Au	(111)	0.69	0.44	0.41 (0.35)	0.60 (0.99)
$a_{fcc} = 4.05 \text{ \AA}$	(001)	0.73	0.46	0.24 (0.26)	2.37 (2.14)
Pd/Pt	(111)	0.62	0.71	0.55 (0.54)	0.30 (0.33)
$a_{fcc} = 3.89 \text{ \AA}$	(001)	0.58	0.70	0.52 (0.51)	0.37 (0.39)
W/Mo	(001)	0.45	0.59	0.42 (0.42)	0.42 (0.42)
$a_{bcc} = 3.16 \text{ \AA}$	(110)	0.40	0.54	0.37 (0.38)	0.52 (0.47)
Cu/Co	(111)*	0.56	0.47	0.43 (0.43)	0.34 (0.35)
majority	(001)	0.55	0.49	0.46 (0.45)	0.26 (0.27)
$a_{fcc} = 3.61 \text{ \AA}$	(110)	0.59	0.50	0.46 (0.46)	0.35 (0.35)
Cu/Co	(111)*	0.56	1.05	0.36 (0.31)	1.38 (1.82)
minority	(001)	0.55	1.11	0.32 (0.32)	1.79 (1.79)
$a_{fcc} = 3.61 \text{ \AA}$	(110)	0.59	1.04	0.31 (0.35)	1.89 (1.55)
Cr/Fe	(111)	0.61	0.82	0.27 (0.31)	2.22 (1.84)
majority	(001)	0.64	0.82	0.11 (0.25)	7.46 (2.55)
$a_{bcc} = 2.87 \text{ \AA}$	(110)*	0.59	0.78	0.22 (0.27)	3.04 (2.18)
Cr/Fe	(111)	0.61	0.41	0.34 (0.34)	0.93 (0.95)
minority	(001)	0.64	0.46	0.35 (0.35)	0.98 (0.95)
$a_{bcc} = 2.87 \text{ \AA}$	(110)*	0.59	0.40	0.32 (0.32)	1.03 (1.06)

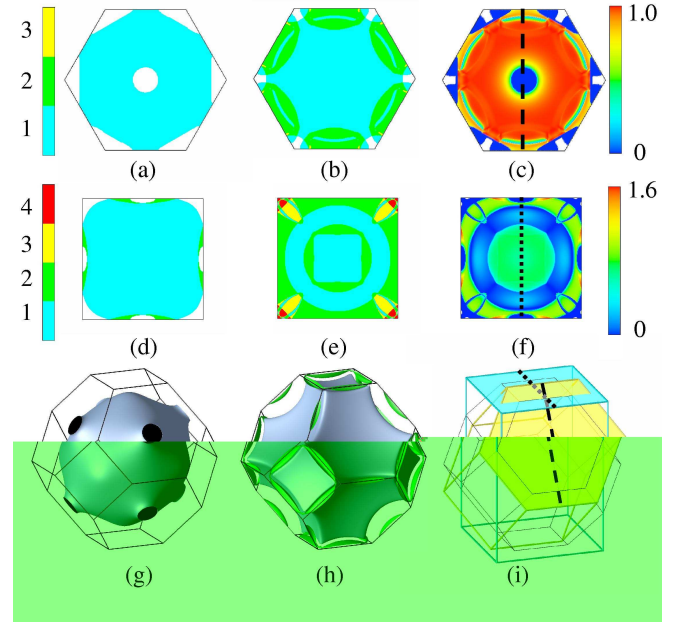


FIG. 1: Top row: Fermi surface projections for (a) Ag, (b) Al and (c) transmission probabilities in 2DBZ for (111) orientation. Middle row: Same for (001) orientation. The colour bars on the left indicate the number of scattering states in the leads for a given two dimensional wavevector $\mathbf{k}_{\parallel}$. The transmission probabilities indicated by the colour bars on the right can exceed 1 for $\mathbf{k}_{\parallel}$ s for which there is more than one scattering state in both Ag and Al. Bottom row: Fermi surfaces of (g) Ag and (h) Al, (i) the interface adapted BZ for (001) and (111) orientations. The vertical dashed line in (c) and on the yellow plane in panel (i) indicate the cross-section used in the left-hand panel of Fig. 2 while the vertical dotted line in (f) and on the blue plane in panel (i) indicate the cross-section used in the right-hand panel.

tance itself tends to be slightly smaller than the lower of the two Sharvin conductances. For these systems the behaviour of the transmission appears to be determined by the projection of the Fermi surfaces. However, this is not so for Al/Ag and Al/Au interfaces. Here we observe a large anisotropy in the transport properties. The factor 2 difference in transmission between (111) and (001) orientations [19] results in a factor 4 difference between interface resistances estimated using the method of [2, 4].

The transmission probability for the (111) and (001) orientations is plotted in Figs. 1c and 1f as a function of the wave-vector component parallel to the interface, $\mathbf{k}_{\parallel}$, within the 2D interface Brillouin zones (BZ). A qualitative difference between the two orientations can be observed. In the (111) case, the transmission is almost uniformly high wherever there are states on both sides of the interface. The (001) orientation exhibits more variation with high transmission in the central and outer regions of the 2D BZ but much lower in a ring-shaped region in between. The presence of this “cold ring” is the reason why the total transmission is lower for the (001) orientation.

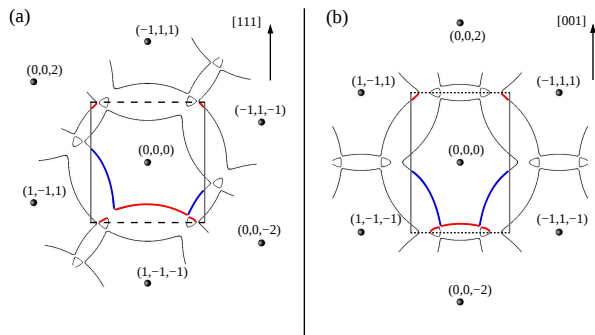


FIG. 2: Intersection of a (110) plane with the Al Fermi surface and with the interface adapted BZs indicated in Fig. 1i (where the meaning of the dashed and dotted lines is explained). The labelled dots indicate the positions of the RL sites with coordinates given in units of $2\pi/a$. The red (blue) lines indicate regions of high (low) transmission.

Explaining the transparency anisotropy of Al/Ag interfaces requires finding an explanation for the low transmission values in this region of the 2D BZ.

Two mechanisms are usually taken into account when analysing the scattering at perfect interfaces. The first, velocity mismatch, is the modulation of the transmission by a factor reminiscent of the free electron formula for the transmission through a potential step: $T = 4v_L v_R / (v_L + v_R)^2$ where $v_{L/R}$ are the components of the Fermi velocities in the transport direction on the left and right sides of the interface. This modulation is indeed present in our calculated transmissions but its effect tends to be noticeable only when one of the velocities is almost vanishingly small. Naive application of the free electron formula yields uniformly good transmission [20] independent of the orientation. Symmetry mismatch, the second mechanism, can suppress the transmission between states of incompatible symmetries (e.g. even vs. odd etc.). Examination of the eigenvectors demonstrates that this is not the case for the Al/Ag system. For example, states on both sides of the interface, with $\mathbf{k}_{\parallel}$ along the vertical dotted line in Fig. 1f, are even under reflection in the plane defined by this line and the (001) transport direction. Their orbital composition ($s, p_y, p_z, d_{yz}, d_{3z^2-r^2}, d_{x^2-y^2}$ where the y axis is parallel to the dotted line and z is the transport direction) is essentially the same for both materials. The same holds for states along other symmetry lines/planes and general $\mathbf{k}_{\parallel}$ points (in the sense of orbital composition). The origin of the “cold ring” must be sought elsewhere.

In spite of the failure of the free electron transmission formula, this simple model serves as a useful starting point for analysing the Fermi surface (FS) topologies. In the simplest possible approach, we model the FS of Ag (shown in Fig. 1g) as a sphere which fits into the first BZ. A larger sphere, accommodating three electrons, is needed for trivalent Al. In an extended zone scheme,

conservation of momentum parallel to the interface dictates that the transmission through a specular interface is non-zero only between states with the same values of $\mathbf{k}_{\parallel}$; these are the $\mathbf{k}_{\parallel}$ -vectors belonging to the region where projections of the Fermi spheres on a plane perpendicular to the transport direction overlap. For systems with lattice periodicity, we must use a downfolded FS, with fragments of the original FS sphere back-translated into the 1st Brillouin zone, a procedure which can be realized geometrically by placing spheres accommodating three electrons on reciprocal lattice (RL) sites and then only considering the fragments in the first BZ. Examination of the FS of Al calculated from first-principles (Fig. 1h) and its cross-section (Fig. 2) reveals that, in spite of its apparent complexity, it remains essentially (piecewise) spherical. For some values of $\mathbf{k}_{\parallel}$ (see Figs. 1b and 1e), Al can now have more than one propagating state. Nevertheless, in the free electron limit, the downfolded states are strictly orthogonal to the states in Ag and the total transmission is unchanged. For a reduced zone scheme, we formulate the following rule: *The transmission between states in two (nearly) free electron materials which have the same $\mathbf{k}_{\parallel}$, but originate from reciprocal lattice sites whose parallel components do not coincide, vanishes in the free electron limit and is expected to be strongly suppressed for nearly free electron like materials.*

Obviously, the truly free electron system can not exhibit anisotropy. However, in the presence of the periodic potential the original, piecewise-spherical Fermi surface and consequently the transmission is going to be modified. Firstly, since the wave functions are no longer pure plane waves, the strict orthogonality of the downfolded states is relaxed and the transmission can assume finite although typically small values (hence *suppressed* instead of *zero* in the above rule). Secondly, the shape of the Fermi surface changes with the modifications being strongest in the vicinity of RL planes where, for Al, we observe the opening of gaps between previously connected fragments. The anisotropy is mostly related to this second effect.

In Fig. 2, we show the intersection of the Al FS with a (110) plane. The two plots are rotated so that the vertical axis in Fig. 2a is the [111] direction while in Fig. 2b it is [001]. In both cases the positions of the nearest RL sites (on which spheres are centred) are shown together with the cross-section through the relevant interface-adapted Brillouin zone, which is different for each orientation; see Fig. 1i. We can now readily identify spheres from which various fragments of the Fermi surface originate and mark those fragments with positive (upward) velocities, according to the rule given above, as having high (red) or low (blue) transmissions. In the (001) case, the “high” fragments originate from (0,0,0) and (0,0,-2) centred spheres. Comparing Figs. 1f and 2b, we note that the position of the gaps opened between these spheres by Bragg reflection on the (001) and (00 $\bar{1}$) planes coincides,

in projection along the [001] direction, with the position of the “cold ring” in Fig. 1f. The other states present in this region originate from (1,-1,-1) (and equivalent) centred spheres, are therefore nearly orthogonal to states in Ag centered on (0,0,0) and so have low transmission. In the (111) case however, the large fragments of FS belonging to the same (1,-1,-1) sphere have high transmissions (Fig. 2a) and dominate transport. In addition, the effect of gap-opening is reduced in this orientation because of the rotation. Combination of these two factors results in the almost uniformly high transmission seen in Fig. 1c.

We can now finally identify the origin of the transmission anisotropy for Al/Ag interface. It stems from two factors: (i) the near orthogonality of the downfolded Al states to those belonging to the simple Ag sphere and (ii) the gaps opened in the continuous free electron Fermi surface by the periodic potential. The latter factor is of course related to the symmetry of the underlying crystal lattice and directly responsible for the introduction of the orientation dependence. For Al/Au interfaces, the interface transmissions and resistances are very similar to the Al/Ag case.

The orientation dependence of the interface transmission of six metal pairs with the same structure and lattice parameter was calculated. For *fcc* Ag/Al a factor two difference between the (111) and (001) orientations was found and explained within the free electron model. The predicted anisotropic interface resistance and Andreev reflection (not shown) are not very sensitive to interface disorder and should be observable experimentally.

Acknowledgments :This work is part of the research program of the “Stichting voor Fundamenteel Onderzoek der Materie” (FOM) and the use of supercomputer facilities was sponsored by the “Stichting Nationale Computer Faciliteiten” (NCF), both financially supported by the “Nederlandse Organisatie voor Wetenschappelijk Onderzoek” (NWO). It is also supported by “NanoNed”, a nanotechnology programme of the Dutch Ministry of Economic Affairs. We are grateful to Anton Starikov for permission to use his sparse matrix version of the TB-MTO code.

-
- [1] see the collection of articles, in *Ultrathin Magnetic Structures I-IV*, edited by J. A. C. Bland and B. Heinrich (Springer-Verlag, Berlin, 1994-2005).
 - [2] K. M. Schep, et al., Phys. Rev. B **56**, 10805 (1997).
 - [3] M. D. Stiles and D. R. Penn, Phys. Rev. B **61**, 3200 (2000).
 - [4] K. Xia, et al., Phys. Rev. B **63**, 064407 (2001).
 - [5] J. Bass and W. P. Pratt Jr., J. Magn. & Magn. Mater. **200**, 274 (1999).
 - [6] C. W. J. Beenakker, Rev. Mod. Phys. **69**, 731 (1997).
 - [7] C. Galinon, K. Tewolde, R. Loloee, W. C. Chiang, S. Olsson, H. Kurt, W. P. Pratt Jr., J. Bass, P. X. Xu, K. Xia, et al., Appl. Phys. Lett. **86**, 182502 (2005).
 - [8] N. W. Ashcroft and N. D. Mermin, *Solid State Physics* (Holt-Saunders International Editions, Philadelphia, 1976).
 - [9] I. I. Mazin, Phys. Rev. Lett. **83**, 1427 (1999).
 - [10] I. I. Mazin, A. A. Golubov, and B. Nadgorny, J. Appl. Phys. **89**, 7576 (2001).
 - [11] M. Zwierzycki, et al., Phys. Rev. B **67**, 092401 (2003).
 - [12] K. Xia, et al., Phys. Rev. B **73**, 064420 (2006).
 - [13] G. E. Blonder, M. Tinkham, and T. M. Klapwijk, Phys. Rev. B **25**, 4515 (1982).
 - [14] R. J. Soulen Jr., J. M. Byers, M. S. Osofsky, B. Nadgorny, T. Ambrose, S. F. Cheng, P. R. Broussard, C. T. Tanaka, J. Nowak, J. S. Moodera, et al., Science **282**, 85 (1998).
 - [15] S. K. Upadhyay, et al., Phys. Rev. Lett. **81**, 3247 (1998).
 - [16] O. K. Andersen, O. Jepsen, and D. Glötzl, in *Highlights of Condensed Matter Theory*, edited by F. Bassani, F. Fumi, and M. P. Tosi (North-Holland, Amsterdam, 1985), pp. 59–176.
 - [17] I. Turek, V. Drchal, J. Kudrnovský, M. Šob, and P. Weinberger, *Electronic Structure of Disordered Alloys, Surfaces and Interfaces* (Kluwer, Boston-London-Dordrecht, 1997).
 - [18] Fe/Cr is an exception. For the majority spin channel, a large orientation dependence of the interface transmission is predicted. Unlike in the case of Al/Ag, this result is very sensitive to interface disorder. In addition, a single spin channel cannot be studied directly making it difficult to obtain an unambiguous experimental result.
 - [19] We performed an extensive series of total energy calculations using LDA and GGA approximations to relax the various Al/Ag interfaces. Only a small dependence of the interface energy on the orientation was found. The transport calculations were repeated using the resulting relaxed geometries. The effect on the interface transmission is less than 3% which is negligible on the scale of the predicted factor of two orientation dependence.
 - [20] Moreover the free electron formula would lead to the violation of the unitarity of the scattering matrix (*i.e.* the conservation of particles) whenever there is more than one state on either side of the interface.

[1] see the collection of articles, in *Ultrathin Magnetic Structures I-IV*, edited by J. A. C. Bland and B. Heinrich